


**ISO/TR 10358**

**Resistance To Chemical Corrosion Classification Parameters**

NO.		m.p. °C	b.p. °C	%	T °C	PE- LD	PE- HD	PP	PB	PVC- U	PVC- C	AB S	PV DF	PE -X
1	Acetaldehyde CH <sub>3</sub> CHO	-123	21	40	20 50 60 80	L NS	S L			NS NS NS	NS NS NS	NS NS NS	NS NS NS	
				tg-l	20 50 60 80	L NS	S L		L NS	NS NS		NS NS	NS NS NS NS	
2	CH <sub>3</sub> CONH <sub>2</sub> Acetamide	82	221	5	20 20							S S		
3	Acetic anhydride (CH <sub>3</sub> CO) <sub>2</sub> O	-73	140	tg-l	20 50 60	L NS	S L	S S	S S	NS NS	NS NS	NS NS	NS	
4	Acetic anhydride (CH <sub>3</sub> CO) <sub>2</sub> O	20	202	Tg-s	20 50 60			S L		NS NS	NS NS	NS NS	S	
5	Acetyl chloride		51	tg-l	20 50							NS NS	NS	
6	Acetylene, gas	-84		tg-g	20 60				L NS					
7	CH <sub>3</sub> CHCN Acetonitrile	-82	77	tg-l	20 50		S					NS NS	L	
8	Allyl alcohol CH <sub>2</sub> CHCH <sub>2</sub> OH	-129	97	tg-l	20 50 60	L NS	S S	S S	S S	L NS		NS		NS
9	Air			tg-g	20 50 60 100 140	S S	S S	S S	S S	S S	S S S S	S S	S S S S	
10	Aluminium chloride AlCl <sub>3</sub>			Sta. sol.	20 50 60 80 100	S S	S S	S S	S S	S S	S S S L	S S	S S S S	
11	Ammonia, aqueous			Sta. sol.	20 50 60	S S	S S	S S	S S	S S	S S S	S S	L	
12	(CH <sub>4</sub> )PO <sub>3</sub> Aluminium sulphate			Sta. sol.	20 50 60 100	S S	S S	S S	S S	S S	L L L NS	S S	S S S	



Perfect service system to maximize customer needs.

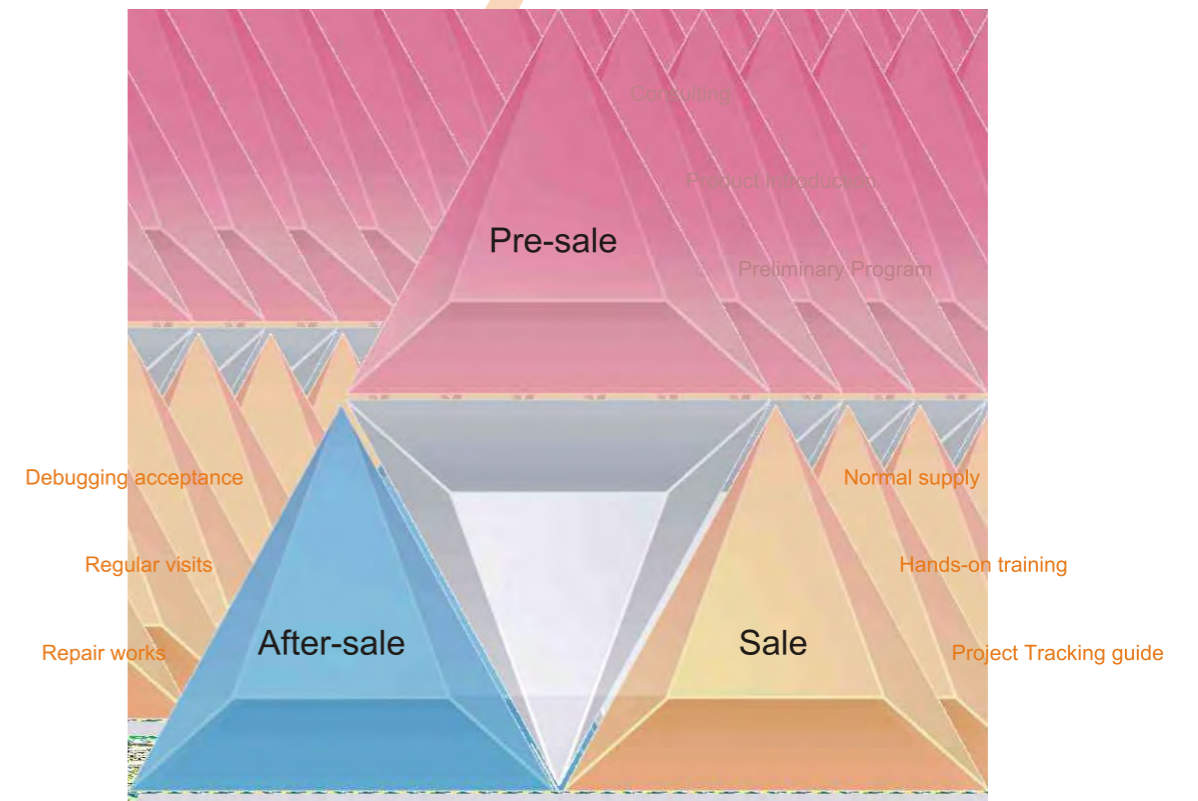



Typical Projects:

Jingsheng Nanhu Bays Oriental Wanda Changsha Business Center Hongfa Long Island Ming Cheng Jia Yuan Friendship Home  
 Dacheng Hua Tian Hotel Roman Holiday Dingwang Building Hunan Provincial Science And Technology Museum Shangcheng Constellation  
 Times Dijing Hotel Suntian Gold Coast Peninsula Holiday Sports New City Longyu Modern City Tianyu International  
 Xiang Li International Metro World Golden Port Jiayuan Xingdian Times Jersey City Zhongtian Plaza Zhujian Huacheng